



# **Biosynthesis of ZnO Nanoparticles Using *Spirulina platensis* Based on Calcination Temperature Changes and Its Antioxidant Activity**

**Lusi Mustika Sari <sup>a</sup>, Yetria Rilda <sup>a\*</sup> and Armaini <sup>a</sup>**

<sup>a</sup> Department of Chemistry, Faculty of Mathematics and Natural Sciences, Andalas University, Padang, West Sumatera-25163, Indonesia.

## **Authors' contributions**

*This work was carried out in collaboration among all authors. All authors read and approved the final manuscript.*

## **Article Information**

DOI: 10.9734/CSJI/2023/v32i4850

## **Open Peer Review History:**

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/102806>

**Original Research Article**

**Received: 02/05/2023**

**Accepted: 04/07/2023**

**Published: 05/07/2023**

## **ABSTRACT**

The effect of different calcination temperatures on molecular structure, morphology, and antioxidant activity was investigated for Zinc Oxide nanoparticles synthesized using the sol-gel method and the capping agent *Spirulina platensis*. The prepared nanoparticle ZnO was calcined at 160°C, 300°C, and 600°C according to the results of the DTA-TGA analysis. The effect of different calcination temperatures on the characterization of the prepared samples was studied using Fourier Transform Infrared (FTIR), X-ray Diffraction (XRD), and Field Emission-Scanning Electron Microscope (FE-SEM). In addition, the potential antioxidant activity of ZnO nanoparticles was investigated using the DPPH method. The results showed that FT-IR and XRD confirmed the presence of ZnO nanoparticles with good purity and small crystal size found in calcified ZnO nanoparticles at 600°C. FE-SEM confirmed the morphology ZnO nanoparticle produced at 600°C calcination are spherics,

\*Corresponding author: E-mail: [yetriarilda@sci.unand.ac.id](mailto:yetriarilda@sci.unand.ac.id), [yetriarilda@yahoo.com](mailto:yetriarilda@yahoo.com);

cubes, and nanorods with different particle sizes with range 50 – 150 nm. ZnO nanoparticles calcined at 600°C also showed higher antioxidant activity when compared to other calcination temperatures.

**Keywords:** Biosynthesis; zinc oxide; capping agent; *Spirulina platensis*; calcinations; antioxidant.

## 1. INTRODUCTION

Nanotechnology is widely used in research to synthesize nanomaterials whose size and shape can be controlled so that they can function as desired [1]. Nanotechnology using environmentally friendly materials is increasingly being developed because it can affect the size and quality of the resulting nanomaterial products and can reduce or eliminate pollution from hazardous materials [2]. Nanomaterials/nanoparticles are nano-sized materials that can be synthesized using a simple method, and the resulting product can be adjusted to the desired morphology [3]. Nanoparticles have unique characteristics, such as large surface area, high reactivity, and high catalytic efficiency. Because they have a very small size (high surface area), nanoparticles have high absorption and efficiency compared to their bulk materials [4].

Nanomaterials with environmentally friendly methods (green method) can be synthesized by various methods such as sol-gel [5], hydrothermal [6], solvothermal [7], and precipitation [8]. The synthesis of nanoparticles using the sol-gel method is a cheap and simple method with many advantages, including producing high-quality nanoparticles, relatively low processing temperatures, and the resulting nanoparticles being more homogeneous [9]. Biosynthesis with the green method usually involves natural ingredients as capping agents. Capping agents are very important as stabilizers that prevent their aggregation/coagulation and steric hindrance in the synthesis of nanoparticles, change the biological activity and surface chemistry, and stabilize the interactions of nanoparticles in the prepared media [10,11]. The capping agent must be biodegradable, well dispersed and soluble, biocompatible, and non-toxic so that the waste material does not damage the environment [10]. Capping agents commonly used are carbohydrates (glucose, lactose, sucrose, fructose, cellulose, starch, and chitosan), proteins (collagen, enzymes, and albumin), amino acids (protein and non-protein), lipids, honey, nucleic acids (DNA), and biological extracts (plants, algae, bacteria, viruses, and fungi) [11]. Recently, algae have often been used

as a capping agent in the synthesis of nanoparticles. Algae can be used in nanoparticle biosynthesis in intercellular or extracellular ways, depending on their cellular reactions within the cell, their primary and secondary metabolites, or the extraction of other algal contents. Algae are autotrophic unicellular or multicellular organisms categorized between prokaryotes and eukaryotes. Its size varies between microalgae (microscopic) and macroalgae (large size), and it has been classified into Bacillariophyta, Chlorophyta, Chrysophyta, Cyanophyta, Dinophyta, Phaeophyta, and Rhodophyta [12]. *Spirulina platensis* is a cyanobacterium known as blue-green microalgae, which has important appeal as a natural source of bioactive compounds with a range of biological activities such as antimicrobial, antiviral, anticancer, antioxidant, and anti-inflammatory [13]. *Spirulina platensis* lives naturally in tropical and subtropical lakes with high pH and high carbonate and bicarbonate concentrations [14]. Mostafa M. El-Sheekh et al. (2022), reported that nanoparticles synthesized with microalgae can be applied as drug delivery and biosensors which can be used in tissue engineering, tumor destruction, anticancer treatment, antimicrobial, biosensors, food preservation and packaging, water treatment, and many other applications that can improve human life [12].

ZnO nanoparticles have received extraordinary attention because of their potential use as chemotherapeutic agents (anticancer) and antimicrobials, and antioxidants because ZnO nanoparticles are capable of absorbing UV rays and have high photostability [15,16]. ZnO nanoparticles are included in the category of metal oxides which are generally recognized as safe metal oxides (generally recognized as safe-GRAS) [15]. A.M. Ismail et al., (2019) reported that the effect of different calcination temperatures will affect the purity of the resulting ZnO nanoparticles, crystal size, and morphology of the product produced [4]. In this research, the synthesis of ZnO nanoparticles was carried out using the sol-gel method and *Spirulina platensis* as a capping agent, with different calcination temperatures of 160°C, 300°C, and 600°C. The

resulting ZnO nanoparticles will be studied for their antioxidant activity.

## 2. METHODOLOGY

### 2.1 Preparation of *Spirulina platensis*

One liter of *Spirulina platensis* was added to bottles containing 10 liters of water. Then, fertilizer, KCL, NPK, ZA, urea, baking soda, and table salt were added and stirred until completely dissolved. The bottle was installed with an air bubble and kept for  $\pm$  10 days. After 10 days, *Spirulina platensis* was harvested by filtering water in nursery bottles, and the biomass was collected to the Petri dish, then dried at room temperature. The dried biomass was milled to obtain *Spirulina platensis* powder.

### 2.2 Biosynthesis of ZnO Nanoparticles

ZnO was synthesized with 0.126 M  $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  and 0.25 M citric acids ( $\text{C}_6\text{H}_8\text{O}_7$ ) in 100 mL of distilled water and stirred at 70°C for 2 hours to form a solution. Subsequently, the solution was placed in the oven at 100- 110°C for 5 hours for gel formation. The 1M NaOH solution was dripped directly into the gel with constant stirring, and the pH of the suspension was adjusted to 9, and stirred for 2 hours. Afterward, ZnO seeds, 1.089 grams of *Spirulina platensis*, and 5% PEG were added and stirred for 2 hours. Then, the resulting suspension ( $\pm$ 100 mL) was transferred into a Teflon-coated stainless-steel autoclave and heated at 160°C for 12 hours. The product was dried and calcinated at 300 and 600°C for 4 hours [17]. ZnO nanorods were characterized using DTA-TGA, FTIR, XRD, and FE-SEM.

### 2.3 Antioxidant Activity

A total of 0.1 g of ZnO-NPs was added to 1 mL of a methanol solution containing the DPPH radical (2,2-diphenyl-1-picryl hydroxyl) (0.012 g/100 mL). The solutions were mixed until homogeneous and then incubated for 30 minutes at room temperature in a dark room. The absorbance was then read at 517 nm against a blank. DPPH solution and ascorbic acid were used as a control and positive control, respectively. The scavenging ability was calculated using the following equations [18]:

$$\text{Scavenging activity} = \frac{A_{517 \text{ control}} - A_{517 \text{ sample}}}{A_{517 \text{ control}}} \times 100\%$$

## 3. RESULTS AND DISCUSSION

### 3.1 DTA-TGA (Thermogravimetric Analysis - Differential Thermal Analyzer)

The DTA-TGA data were taken at a temperature range of 30°C to 800°C and the ZnO nanoparticle samples had been dried at 100°C. The TGA pattern in Fig. 1 illustrates an overall weight/mass reduction of 63% which results in excellent thermal stability of the synthesized ZnO nanoparticles. This proves that mass reduction 33 consists of four distinct stages, which are shown together with their respective endothermic peaks in the DTA spectrum. In the temperature range of 30-200°C there was a mass decrease of 20% and the endothermic peaks at 100°C and 190°C indicated the loss of water content and volatile components on the surface of the ZnO nanoparticles. The mass is reduced by 12% in the next step over a temperature range of 270-340°C with an endothermic peak at 312°C. In this range, the weight loss is caused by the loss of amine compounds, hydroxyl, and some carboxyl compounds according to the FTIR analysis in Fig. 1. The next weight loss occurs in the temperature range of 340-430°C by 29% and the endothermic peak is at 400°C, which is a decrease in the mixture of organic residues. The reduction of organic residues was continued at a temperature range of 430-500°C by 2% and there was no further reduction in the mass of ZnO nanoparticles up to a temperature of 700 °C which indicated that the thermal stability of the formation of ZnO nanoparticles had been achieved. Based on the pattern of TGA and DTA, the calcination temperature was chosen at 600°C. The stages of mass reduction are in accordance with those reported by R. Vinayagam et al. (2022) who synthesized ZnO anoparticles using *Muntingia calabura* leaf extract [19].

### 3.2 FTIR (Fourier Transform Infra-red)

The FTIR characterization of the ZnO NPs product aims to identify the functional groups present in the *Spirulina platensis* microalgae and the biosynthetic products. In Fig. 2, it can be seen how the stability of the capping agent of the microalgae *Spirulina platensis* when used for ZnO biosynthesis at pH 9 is affected by temperature. At a temperature of 160°C (hydrothermal yield), there are still organic compounds marked by an absorption peak at

wave numbers  $3402.18\text{ cm}^{-1}$ ;  $2876.47\text{ cm}^{-1}$ ;  $1577.93\text{ cm}^{-1}$ ;  $1368, 62\text{ cm}^{-1}$ ;  $1100.51\text{ cm}^{-1}$  and  $837.31\text{ cm}^{-1}$ . This absorption peak is the same as the peak of *Spirulina platensis* as shown in Fig. 2. Whereas ZnO nanoparticles at a temperature of  $300^\circ\text{C}$  show that many organic compounds have been lost during heating, and there are still carboxyl groups ( $-\text{CO}$ ) at wave number  $1422.52\text{ cm}^{-1}$  and stretching of

the amide group  $\text{C}=\text{O}$ , vibration of the  $\text{C}=\text{C}$  carbonyl stretch, and symmetrical or asymmetric stretching of the carboxylate and  $\text{C}-\text{O}$  groups at wave number  $869.50\text{ cm}^{-1}$ . Calcination at  $600^\circ\text{C}$  has no visible absorption peaks, which indicates that the organic compounds and other impurities are gone and pure ZnO nanoparticles have been formed.

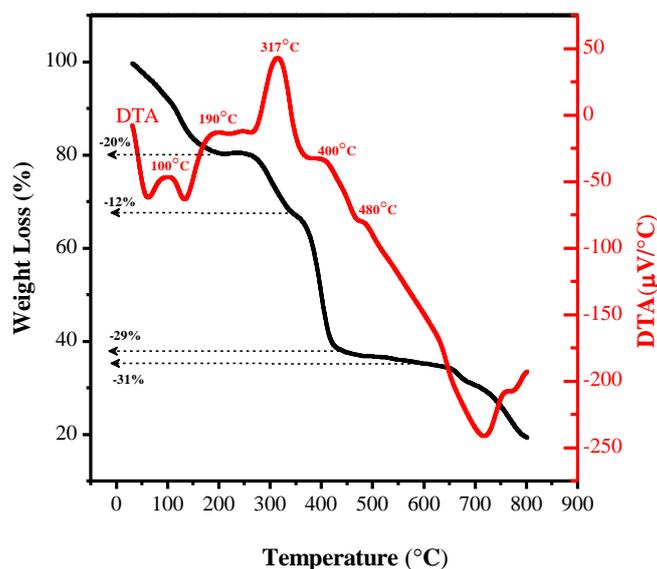


Fig. 1. TGA-DTA pattern of ZnO nanoparticles synthesized with *Spirulina platensis* as a capping agent

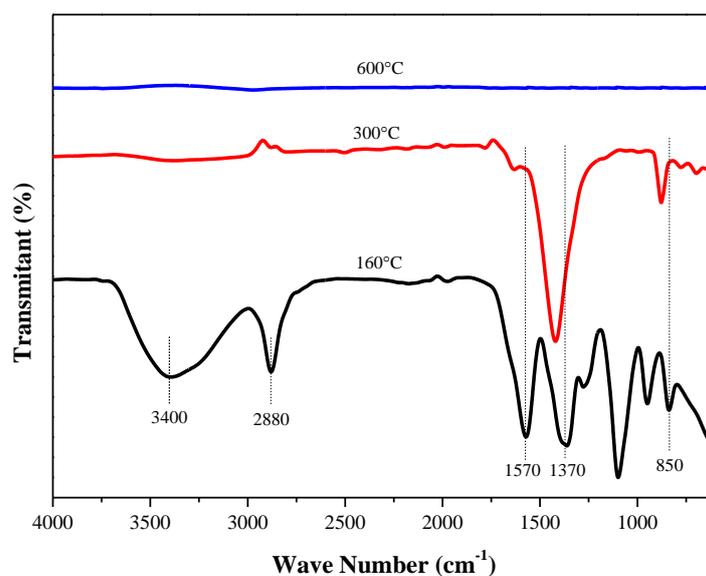


Fig. 2. FTIR spectrum of ZnO synthesized at pH 9 at temperatures of  $160^\circ\text{C}$ ,  $300^\circ\text{C}$  and  $600^\circ\text{C}$

### 3.3 XRD (X-ray Diffraction)

In Fig. 3, it can be seen that after the hydrothermal process, ZnO crystals have formed at angles of  $2\theta$   $31.74^\circ$ ;  $34.40^\circ$ ;  $36.23^\circ$ ;  $47.53^\circ$ ;  $56.59^\circ$ ;  $62.86^\circ$ ;  $66.38^\circ$ ;  $67.96^\circ$  and  $69.10^\circ$ , but there are still other peaks at angles of  $2\theta$   $19.11^\circ$  and  $23.53^\circ$  which are the peaks of polyethylene glycol (PEG), and peaks at  $2\theta$   $32.93^\circ$  and  $39.46^\circ$  which are the peaks of  $\text{Zn(OH)}_2$ . After calcining at  $300^\circ\text{C}$ , the PEG peak has disappeared and the  $\text{Zn(OH)}_2$  peak is still present at an angle of  $2\theta$   $30.01^\circ$ ;  $33.00^\circ$ ;  $37.87^\circ$ ;  $39.78^\circ$  and  $41.45^\circ$ . Whereas after calcining at  $600^\circ\text{C}$ , no other peaks associated with impurities appeared, indicating that high-purity ZnO nanoparticles had been obtained. In addition, the peak of ZnO nanoparticles at  $600^\circ\text{C}$  is also higher, sharper, and has a small FWHM intensity. Akbarian (2018) reported that the smaller the FWHM and the higher the peak intensity, the higher the crystallinity [20]. The sharp and narrow peaks on the ZnO nanoparticle samples which were calcined at  $600^\circ\text{C}$  prove that the nanoparticles have high crystallinity when compared to the ZnO nanoparticle samples which yielded hydrothermal at  $160^\circ\text{C}$  and calcination at  $300^\circ\text{C}$ . The XRD pattern of the synthesized metal oxide ZnO at a calcination temperature of  $600^\circ\text{C}$  can be observed, where the intensity is at  $2\theta = 31.74^\circ$ ;  $34.40^\circ$ ;  $36.23^\circ$ ;

$47.53^\circ$ ;  $56.59^\circ$ ;  $62.86^\circ$ ;  $66.38^\circ$ ;  $67.96^\circ$  and  $69.10^\circ$  show the crystal structure of ZnO is wurtzite and have crystal planes with hkl values (100), (002), (101), (102), (110), (200), (112), and (201) with the hexagonal unit cell conforms to the ICSD standard - 15772476.

### 3.4 FE-SEM (Field Emission-Scanning Electron Microscope)

FE-SEM is an electron microscope that images the surface of a sample by scanning it with high-emission electrons. Field Emission Scanning Electron Microscopy (FE-SEM) analysis is used to determine the surface morphology with a certain magnification and particle size distribution. Fig. 4 (a) below shows the FE-SEM pattern of ZnO nanoparticles after being calcined at  $600^\circ\text{C}$ . This figure shows that the ZnO nanoparticles produced have various morphologies, namely nanocubes, nanospheres, and nanorods. There is a lot of agglomeration, hence, the morphology formed is not clearly visible. Agglomeration usually occurs during the synthesis of NPs in aqueous media. It also occurs due to polarity, electrostatic attraction, and high surface energy of ZnO-NPs Fig. 4 (b) shows the particle sizes of ZnO nanoparticles are in range of 50 - 150 nm.

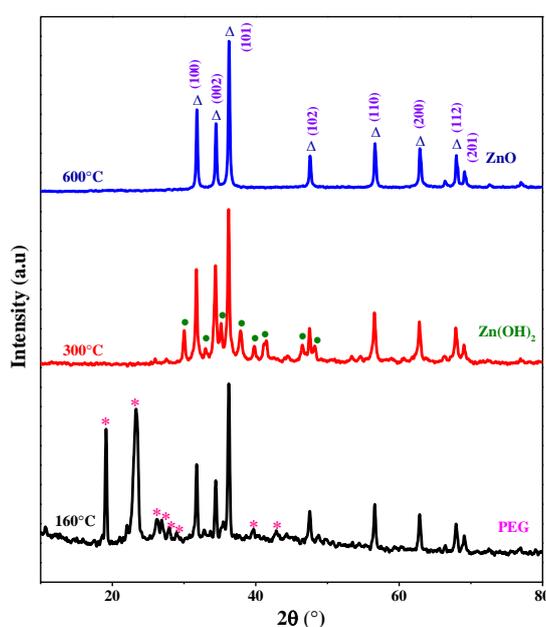


Fig. 3. XRD diffraction pattern of ZnO nanoparticles at a temperature calcination of  $160^\circ\text{C}$ - $600^\circ\text{C}$  (Rev: hkl on picture added)

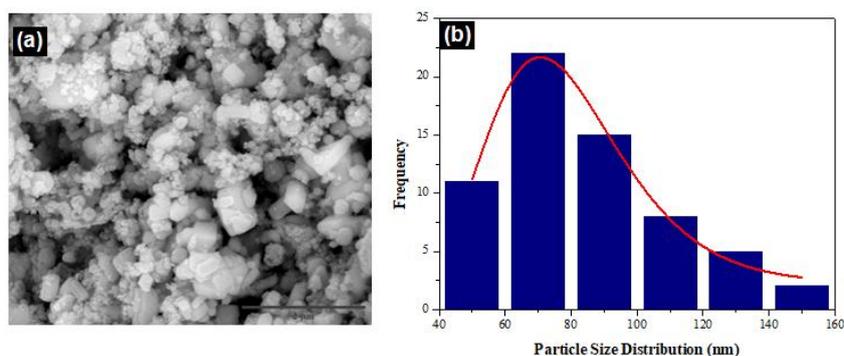


Fig. 4. FE-SEM pattern of ZnO nanoparticles (a) and particle size distribution (b) from calcination at 600°C



Fig. 5. DPPH with dark purple color changed to yellow color after added by ZnO nanoparticle

Table 1. Antioxidant activity of ZnO nanoparticles

Calcination Temperature	Antioxidant Activity (%)
160°C	63,9
300°C	72,1
600°C	84,0
Ascorbic acid	98,3
<i>Spirulina platensis</i>	54,4

### 3.5 Antioxidant Activity

Determination of antioxidant levels aims to see the ability of ZnO to scavenge free radicals from DPPH (2,2-diphenyl-1-picrylhydrazyl). DPPH is a stable radical whose color is dark purple and will turn yellow when reduced by other substances or other radicals as show at Fig. 5. In Table 1, the antioxidant activity of ZnO calcined at 600C shows a higher number, namely 84.0%. Ascorbic acid was used as a control, with an antioxidant level of 98.3%.

## 4. CONCLUSION

ZnO nanoparticles have been successfully synthesized using the sol-gel method with the addition of *Spirulina platensis* as a capping

agent. The difference in calcination temperature affects the purity and crystal size of the resulting ZnO nanoparticles. Calcination at 600°C showed high purity of ZnO nanoparticles, high crystallinity, and smaller crystal size than other calcination temperatures. ZnO nanoparticles resulting from calcination at 600°C also showed high antioxidant activity of 84.0%.

## COMPETING INTERESTS

Authors have declared that no competing interests exist.

## REFERENCES

1. Yulianto B et al. Green synthesis of metal oxide nanostructures using naturally

- occurring compounds for energy, environmental, and bio-related applications, *New J. Chem.* 2019;43(40): 15846–15856.  
DOI: 10.1039/c9nj03311d
2. Khalafi T, Buazar F, Ghanemi K. Phycosynthesis and Enhanced Photocatalytic Activity of Zinc Oxide Nanoparticles Toward Organosulfur Pollutant. *Sci. Rep.* 2019;9(1):1–10.  
DOI: 10.1038/s41598-019-43368-3
  3. Hulkoti NI, Taranath TC. Biosynthesis of nanoparticles using microbes-A review, *Colloids Surfaces B Biointerfaces.* 2014;121:474–483.  
DOI: 10.1016/j.colsurfb.2014.05.027
  4. Ismail AM, Menazea AA, Kabary HA, El-shebiny AE, Samy A. The influence of calcination temperature on structural and antimicrobial characteristics of zinc oxide nanoparticles synthesized by Sol e Gel method, *J. Mol. Struct.* 2019;1196: 332–337.  
DOI: 10.1016/j.molstruc.2019.06.084
  5. R. Dadi, R. Azouani, M. Traore, C. Mielcarek, and A. Kanaev, Antimicrobial activity of ZnO and CuO nanoparticles against gram positive and gram negative strains, *Mater. Sci. Eng. C.* 2019; 104:109968.  
DOI: 10.1016/j.msec.2019.10996
  6. Gerbreders V et al. Hydrothermal synthesis of ZnO nanostructures with controllable morphology change, *CrystEngComm.* 2020;22(8):1346–1358.  
DOI: 10.1039/c9ce01556f
  7. Zare M, Namratha K, Byrappa K, Surendra DM, Yallappa S, Hungund B. Surfactant Properties Assisted Solvothermal Synthesis of ZnO Nanoparticles and Study of their Antimicrobial and Antioxidant, *J. Mater. Sci. Technol;* 2017.  
DOI: 10.1016/j.jmst.2017.09.014.
  8. Adam RE, Pozina G, Willander M, Nur O. Synthesis of ZnO nanoparticles by co-precipitation method for solar driven photodegradation of Congo red dye at different pH,” *Photonics Nanostructures - Fundam. Appl.* 2018;32: 11–18.  
DOI: 10.1016/j.photonics.2018.08.005
  9. Parashar M, Shukla VK, Singh R. Metal oxides nanoparticles via sol–gel method: a review on synthesis, characterization and applications, *J. Mater. Sci. Mater. Electron.* 2020;31(5):3729–3749.  
DOI: 10.1007/s10854-020-02994-8
  10. Javed R, Zia M, Naz S, Aisida SO, Ain N, Ao Q. Role of capping agents in the application of nanoparticles in biomedicine and environmental remediation: recent trends and future prospects, *J. Nanobiotechnology.* 2020;1–15.  
DOI: 10.1186/s12951-020-00704-
  11. Sidhu AK, Verma N, Kaushal P. Role of Biogenic Capping Agents in the Synthesis of Metallic Nanoparticles and Evaluation of Their Therapeutic Potential. 2022;3:1–17.,  
DOI: 10.3389/fnano.2021.801620
  12. El-sheekh MM, Morsi HH, Hassan LHS, Ali SS. The efficient role of algae as green factories for nanotechnology and their vital applications, *Microbiol. Res.* 2022; 263:127111.  
DOI: 10.1016/j.micres.2022.127111
  13. Ismail GA, El-sheekh MM. Antimicrobial, Antioxidant Antiviral Activities of Biosynthesized Silver Nanoparticles by Phycobiliprotein Crude Extract of the Cyanobacteria *Spirulina platensis* and *Nostoc linckia*; 2021.
  14. Sharma G, Jasuja ND, Kumar M, Ali MI. Biological Synthesis of Silver Nanoparticles by Cell-Free Extract of *Spirulina Platensis*; 2015.
  15. Asif N, Fatima S, Aziz N, Zaki A, Fatma T. Bioorganic Chemistry Biofabrication and characterization of cyanobacteria derived ZnO NPs for their bioactivity comparison with commercial chemically synthesized nanoparticles, *Bioorg. Chem.* 2021; 113:104999.  
DOI: 10.1016/j.bioorg.2021.104999.
  16. Javed R, Usman M, Tabassum S, Zia M. Effect of capping agents: Structural, optical and biological properties of ZnO nanoparticles, *Appl. Surf. Sci.* 2016; 386:319–326.  
DOI: 10.1016/j.apsusc.2016.06.042
  17. Zhao X, Li M, Lou X. Sol-gel assisted hydrothermal synthesis of ZnO microstructures: Morphology control and photocatalytic activity, *Adv. Powder Technol.* 2014;25(1):372–378.  
DOI: 10.1016/j.appt.2013.06.004
  18. Sharmila G, Thirumarimurugan M, Muthukumaran C. Green synthesis of ZnO nanoparticles using *Tecoma castanifolia* leaf extract: Characterization and evaluation of its antioxidant, bactericidal and anticancer activities, *Microchem. J.* 2018;145:578–587.

- DOI: 10.1016/j.microc.2018.11.022.
19. Vinayagam R et al. Rapid photocatalytic degradation of 2, 4-dichlorophenoxy acetic acid by ZnO nanoparticles synthesized using the leaf extract of *Muntingia calabura*, *J. Mol. Struct.* 2022; 1263:133127.  
DOI: 10.1016/j.molstruc.2022.133127
20. Akbarian M, Mahjoub S, Elahi SM, Zabihi E, Tashakkorian H. *Urtica dioica* L. extracts as a green catalyst for the biosynthesis of zinc oxide nanoparticles: Characterization and cytotoxic effects on fibroblast and MCF-7 cell lines, *New J. Chem.* 2018;42(8):5822–5833.  
DOI: 10.1039/c8nj00496j

© 2023 Sari et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

*Peer-review history:*

*The peer review history for this paper can be accessed here:*  
<https://www.sdiarticle5.com/review-history/102806>